



Solvent-free synthesis of cyclic carbonates from CO₂ and epoxides catalyzed by reusable alumina-supported zinc dichloride

Grigoriy N. Bondarenko^a, Ekaterina G. Dvurechenskaya^a, Olga G. Ganina^a, Francisco Alonso^{b,*}, Irina P. Beletskaya^{a,*}

^a Department of Chemistry, Lomonosov Moscow State University, 1 Leninskie Gory, GSP-2, 119992 Moscow, Russia

^b Instituto de Síntesis Orgánica (ISO) and Departamento de Química Orgánica, Facultad de Ciencias, Universidad de Alicante, Apdo. 99, 03080, Alicante, Spain

ARTICLE INFO

Keywords:

Carbon dioxide
Epoxide
Zinc dichloride/alumina
Cyclic carbonate
Heterogeneous catalysis

ABSTRACT

There is an ongoing interest to advance in the production of cyclic carbonates from carbon dioxide and epoxides under sustainable conditions. The ZnCl₂/Al₂O₃-TBAI system has evinced to be a cheap, simple, readily accessible and reusable catalyst for the reaction of carbon dioxide with aromatic, aliphatic, cyclic and fluorinated epoxides with a low metal loading under solvent-free and mild conditions. This system has been also shown to be adequate for the reaction of epoxides with carbon disulfide to form the sulfur-containing cyclic carbonate analogs.

1. Introduction

Carbon dioxide is, among others (CO, CO₂, CH₄), the most appealing C1 carbon source because of being renewable, nontoxic, non-flammable, readily available and relatively inexpensive. It can be converted into fuels, materials and value-added chemicals by replacing other environmentally less benign substances with a lower E-factor impact [1]. It is a crucial building block for the synthesis of useful organic compounds [2–5], being its reaction with epoxides [6,7] of paramount importance for the industrial preparation of carbonates (e.g., dimethyl carbonate, diphenyl carbonate, ethylene carbonate, propylene carbonate and glycerol carbonate) [8,9] and polycarbonates [10]. Cyclic carbonates, apart from being present in natural products and potential pharmaceuticals, have found manifold applications in different disciplines; for instance, as electrolytes in lithium-ion batteries, as polar aprotic solvents and as synthetic intermediates [11–14].

Besides being a 100% atom-economical process, the high thermodynamic stability of the CO₂ molecule [15] makes the intervention of catalysts imperative for activating the implicated reagents [16]. Homogeneous catalysis and, to some extent, organocatalysis, dominate over heterogeneous catalysis, typically, in the presence of an ammonium salt [6,17–19]. A great advance in the field was made by North et al., who introduced the binuclear Al-salen [20,21] and salphen [22,23] complexes, together with a polystyrene-immobilized counterpart [24], as highly efficient catalysts for the carboxylation of terminal epoxides at room temperature and atmospheric pressure. Notwithstanding this research merit, the catalysts preparation requires

multistep synthesis and the immobilized catalyst suffers from deactivation. Mononuclear Al-salen complexes [25] were shown to be also effective in the carboxylation of terminal epoxides, though higher temperature and longer reaction time were mandatory.

Lately, new catalytic systems have emerged with the aim to upgrade the performance of the epoxide – CO₂ cycloaddition, namely: CaI₂-(PEG DME 500) [26], CaI₂-crown ether [27,28], tri-Co complex containing amine-bis(benzotriazole phenolate) ligands (in combination with TBAC) [29], highly active Al-aminotriphenolate [30] and Al-porphyrin based catalysts [31], Mn(II)-pyridin-4-yl-phosphonate MOF-TBAB [32], Ln(III)-coordinated polymers-TBAB [33] and La-heteroscorpionate-TBAB [34]. Notably, the formation of the cyclic carbonates could be accomplished not only in the presence of rather sophisticated complexes but also with simple catalysts such as MgCl₂ (DMF, 100 °C) [35].

The combination of a ZnX₂ Lewis acid catalyst with an ammonium salt has been also successfully exploited in the epoxide carboxylation [36]. For instance, TBAI with Zn-salphen [37,38], bis-(Zn-salphen) [39], Zn-azatrane [40], Zn-pyrrolidine [41] complex or Zn-MOF [42,43] allowed to carry out the reaction under mild conditions in good yields. The ammonium salt could be replaced with an ionic liquid [44] to furnish good yields with the assistance of a ligand-free zinc salt at 30 °C and 1 atm CO₂ [45]. Ema et al. inserted an ammonium-fragment linker into zinc porphyrinate [46–48], with the resulting catalyst showing high TONs and TOFs, albeit under harsh reaction conditions (120 °C, 17 atm). A system based on the Zn cluster Zn₄(TFA)₆O-TBAI, insensitive to moisture and gaseous impurities, was effective under mild conditions (25 °C, 1 atm) but relatively longer reaction time was needed

* Corresponding author.

E-mail addresses: faalonso@ua.es (F. Alonso), beletska@org.chem.msu.ru (I.P. Beletskaya).

<https://doi.org/10.1016/j.apcatb.2019.04.024>

Received 25 February 2019; Received in revised form 2 April 2019; Accepted 9 April 2019

Available online 28 April 2019

0926-3373/ © 2019 Elsevier B.V. All rights reserved.

(up to 20 h) [49]. As an alternative to the activation of the epoxide, CO₂ can be activated by N-heterocyclic carbenes (NHC) through the formation of NHC–CO₂ adducts [50]; in this sense, the NHC–ZnBr₂ system catalyzed the cycloaddition of CO₂ to epoxides at atmospheric pressure (80 °C, DMSO) [51].

Metal-free organocatalytic systems look very attractive and green [18]. As recent examples, highly active cavitand-based polyphenol catalyst allowed to get good-to-excellent yields of both mono- and disubstituted carbonates in 18 h at 50 °C and 10 bar of CO₂ in the presence of TBAI [52]; using squaramide derivatives, terminal carbonates were obtained in shorter time at higher temperature [53], whereas harsher conditions were necessary for internal epoxides. Alkyl ammonium and phosphonium salts themselves are active organocatalysts but they are difficult to recover and are deployed in quasi-equimolar amounts with respect to the substrate.

In spite of the fact of the good catalytic behavior manifested by the aforementioned catalysts, their homogeneous nature precludes reutilization and limits their practical application, especially of those involving tedious preparation procedures. In this vein, heterogeneous catalysis offers the possibility of catalyst recovery and reuse, hence making the whole process more sustainable [54]. Even though heterogeneous catalysts are characterized by a longer life than the homogeneous counterparts, the former have been much less investigated than the latter in the epoxide carboxylation, in part, because they are considered less active and require more severe conditions to reach a satisfactory yield. For instance, the silica/TBAB-catalyzed CO₂-epoxide cycloaddition needed high catalyst loading, pressure (40 atm) and temperature (90 °C) [55]. Likewise, elevated temperature (100–140 °C) and pressure (10–45 atm) or prolonged reaction time (up to 48 h) had to be applied for ionic liquids [56] grafted onto different supports [57–61]. A Cu^{II} metal-organic hydrogel [62] and indium-based metal organic framework [63] worked under milder conditions but with modest-to-good conversions of the terminal epoxides (32–80%). Recently investigated, the heterogeneous catalysts based on three-dimensional copper-phosphate grid [64], APTES-modified zirconium oxide on MCM-41 [65], and cobalt-coordinated conjugated microporous polymer (Co-CMP-2) [66] allowed to attain high TONs and TOFs, but excellent yields were achieved only under relatively high pressure and temperature (80–100 °C, 10–30 atm). Several zinc-containing heterogeneous systems, such as a zinc complex with mesoporous *o*-hydroxybenzene polymers [67], a zeolitic imidazolate framework (ZIF-95) containing Zn atoms [68], a binuclear supramolecular zinc complex with hexadentate ligands [69] or Zn-Mg-Al composite oxides [70] have been reported; although all the catalysts were reused, at least, five times without significant loss of their activity, the reaction conditions were rather harsh (80–140 °C, 12–50 atm).

Concluding this introduction, we can say that there is a general upsurge of interest in developing sustainable catalysts [71,72] and reaction media [73] to promote the synthesis of cyclic carbonates from CO₂ and epoxides under mild conditions [74]. In an ideal scenario, the catalytic systems should be simple, reusable for several cycles, without toxic reagents, and producing the cyclic carbonates in high yield and selectivity with a minimum generation of waste. In this context, we present herein our endeavor to adhere to these premises and introduce the heterogeneous catalytic system composed of ZnCl₂ supported on alumina which, together with a catalytic amount of TBAI, catalyzes the epoxide carboxylation and thiocarboxylation in an efficient manner.

2. Experimental

2.1. General

All starting materials were purchased from Sigma Aldrich and P&M-Invest (<http://en.fluorine1.ru/>) and were used without any further purification; solvents were dried and deoxygenated using standard procedures. Carbon dioxide gas of 99.99% purity was used. The

carboxylation reactions were performed in a 15 mL-capacity glass low-pressure reactor RLP25ML (<http://www.openscience.ru>) equipped with a gas feeding system, magnetic stirrer and manometer. The NMR spectra of all products were recorded on Bruker Avance 400 and Agilent 400MR spectrometers (¹H NMR 400 MHz, ¹³C NMR 100.6 MHz and ¹⁹F NMR 376 MHz) at ambient temperature in CDCl₃. The chemical shifts are reported in ppm relative to SiMe₄ in the ¹H NMR spectra and to chemical shifts of the solvent peaks, as a secondary standard, in the ¹³C NMR spectra. The chemical shifts are reported in ppm relative to CFCl₃ as an internal standard in the ¹⁹F NMR spectra. The coupling constants (*J*) are given in Hertz. The GLC-mass spectra were obtained on a LECO Pegasus 4D TOF spectrometer with Agilent GC with RTX-5-MS column. Column chromatography was carried out on Merck silica gel 60 (40–63 μm) with petroleum ether (b.p. 60–90 °C) as the eluent.

XRD patterns were recorded on an X-ray diffractometer DRON-3 in the reflection mode with CoKα radiation using θ/2θ scanning technique. FT-IR spectra were obtained in the 750–4000 cm^{−1} spectral range using a Thermo Nicolet 200 FT-IR instrument. Samples of organic products for IR spectroscopy were used as a thin film. FT-IR/ATR spectra of inorganic specimens were recorded in the 400–8000 cm^{−1} spectral range on FT-IR Tensor II spectrometer (Bruker) equipped with single reflection diamond ATR module Platinum (Bruker). Mass spectra were recorded using a Varian 431-GC/220-MS spectrometer with EI (electron ionization). The nitrogen adsorption–desorption isotherms were collected at 77 K using an adsorption analyzer Micromeritics ASAP2020 Plus. The pore size distribution was calculated by the BJH (Barrett-Joyner-Halenda) method using the desorption isotherm. The total pore volume (*V*, mL/g) and the specific surface area (*S*, m²/g) was determined by the BET (Brunauer-Emmett-Teller) method. Scanning electron microscopy (SEM) and energy-dispersive X-ray spectroscopy (EDX) studies were carried out on a LeoSupra 50 VP microscope equipped with an Oxford Instrument XMax detector using a 15 kV accelerating voltage and working distance of 7 nm in a low vacuum mode (N₂, 40 Pa). A VPSE detector was applied with magnifications from 200 to 2500. EDX spectra were recorded using X-Ray microanalysis and, then, assigned to the image of the sample surface. The energy resolution of the EDX detector reached 129 eV for line MnKα (5898.8 eV). The statistical analysis of the obtained micrographs for the determination of the complex composition was performed using ImageJ software.

2.2. Preparation of the Lewis acid/support catalysts

The Lewis acid/support 10 wt% was prepared by grinding the anhydrous Lewis acid (50 mg) with the dry support (450 mg) in agate pounder for 20 min at ambient temperature. The resulting homogeneous powder was heated in vacuum for 2 h at 80 °C.

2.3. General procedure for the reaction of epoxides with CO₂

The epoxide (4.0 mmol), catalyst (0.024 mmol) and quaternary ammonium salt (0.064 mmol) were added to a 25 mL glass low-pressure reactor (RLP25ML, www.openscience.ru) equipped with a gas feeding system, magnetic stirrer and manometer. The reactor was purged thrice followed by the introduction of CO₂ gas (4 atm, unless otherwise specified). The reaction mixture was stirred at 60 °C for 6 h (or under other conditions as indicated below for certain compounds). The resulting mixture was cooled to room temperature, centrifuged (no solvent added) and purified by column chromatography (silica gel, petroleum ether). The isolated product was dried under vacuum.

2.3.1. General procedure for the reaction of epoxides with CO₂ in the presence of solvent

The same general procedure 2.3 was applied but with the addition of solvent (2 mL). After the reaction completion, the resulting mixture was cooled to room temperature, centrifuged, concentrated under vacuum and purified by column chromatography (silica gel, petroleum


ether). The isolated product was dried under vacuum.

2.4. Catalyst reutilization procedure


The reaction was carried out as described above in the general procedure 2.3 with propylene oxide for 2 h. The resulting mixture was centrifuged (no solvent added) and the precipitate was dried under vacuum and added to the reactor together with a new loading of reagents. TBAI was recovered from the supernatant by precipitation with diethyl ether (2 mL), followed by centrifugation and drying under vacuum; then, it was used in the next run.

2.5. Characterization of compounds 2a-o


The NMR spectral data for compounds **2a-k** correspond to those in the literature. (See ESI for more details.)



4-(2,3,3,3-Tetrafluoro-2-(trifluoromethoxy)propyl)-1,3-dioxolan-2-one (2l). (24 h, 80 °C, TBAB as nucleophilic additive). Colorless oil. ^1H NMR (400 MHz, CDCl_3) δ : 5.07–4.99 (m, 1 H), 4.64 (t, J = 8.4 Hz, 1 H), 4.20–4.15 (m, 1 H), 2.82–2.71 (m, 1 H), 2.59–2.49 (m, 1 H). ^{13}C NMR (100 MHz, CDCl_3) δ : 153.6, 119.5 (qd, J = 264.6 Hz, 5.7 Hz), 118.9 (qdq, J = 286.6 Hz, 32.9 Hz, 5.1 Hz), 107.5 (dq, J = 261.4, 38.2 Hz), 70.2, 69.1, 36.9 (dd, J = 21.9 Hz, 7.6 Hz). ^{19}F NMR (376 MHz, CDCl_3) δ : –53.4 – –53.6 (m, 3 F), –83.2 (dd, J = 39.5 Hz, 4.2 Hz, 3 F), –130.4 (ddq, J = 152.6 Hz, 34.5 Hz, 13.2 Hz, 1 F). Anal. calcd for $\text{C}_7\text{H}_5\text{F}_7\text{O}_4$: C, 29.39; H, 1.76; F, 46.48; O, 22.37. Found: C, 29.43; H, 1.79; F, 46.46; O, 22.32. IR ($\bar{\nu}$, cm^{-1}): 773, 850, 881, 889, 937, 1012, 1074, 1103, 1128, 1201, 1265, 1311, 1350, 1392, 1485, 1811, 2931, 2991, 3608. EI-MS (m/z): 284 (M^+ –2, 0.1%), 242 (0.5), 125 (7), 87 (27), 77 (5), 69 (100), 64 (4), 59 (27), 57 (10), 55 (10), 47 (7), 44 (34), 43 (45), 42 (20), 41 (7), 39 (7), 31 (9), 30 (14), 29 (43). (See ESI for spectra).



4-[(1,1,2,2-Tetrafluoroethoxy)methyl]-1,3-dioxolan-2-one (2m). (24 h, 80 °C, TBAB as nucleophilic additive). Colorless oil. ^1H NMR (400 MHz, CDCl_3) δ : 5.75 (tt, J = 52.8 Hz, 2.7 Hz, 1 H), 4.96–4.91 (m, 1 H), 4.55 (t, J = 8.8 Hz, 1 H), 4.34 (dd, J = 9.0 Hz, 5.9 Hz, 1 H), 4.26 (dd, J = 11.7 Hz, 3.1 Hz, 1 H), 4.10 (dd, J = 11.7 Hz, 3.9 Hz, 1 H). ^{13}C NMR (100 MHz, CDCl_3) δ : 154.2, 117.0 (td, J = 270.6 Hz, 28.7 Hz), 107.3 (tt, J = 251.2 Hz, 41.3 Hz), 73.2, 65.5, 63.0 (t, J = 5.3 Hz). ^{19}F NMR (376 MHz, CDCl_3) δ : –91.6 (dtd, J = 145.3 Hz, 5.1 Hz, 2.9 Hz, 1 F), –92.3 (dtd, J = 145.3 Hz, 5.9 Hz, 3.3 Hz, 1 F), –137.0 (dt, J = 52.8 Hz, 5.5 Hz, 2 F). Anal. calcd for $\text{C}_6\text{H}_6\text{F}_4\text{O}_4$: C, 33.04; H, 2.77; F, 34.84; O, 29.34. Found: C, 33.08; H, 2.75; F, 34.81; O, 29.36. IR ($\bar{\nu}$, cm^{-1}): 771, 847, 912, 953, 991, 1049, 1082, 1171, 1209, 1279, 1309, 1402, 1485, 1792, 2357, 2931, 2966, 2999, 3573. EI-MS (m/z): 216 (M^+ –2, 0.2%), 174 (0.5), 158 (1), 144 (2), 131 (11), 101 (69), 93 (11), 87 (95), 86 (8), 82 (7), 67 (4), 57 (11), 51 (74), 44 (49), 43 (100), 42 (13), 31 (24), 30 (13), 29 (82). (See ESI for spectra).



4-[(2,2,3,3-Tetrafluoropropoxy)methyl]-1,3-dioxolan-2-one (2n). (24 h, 80 °C, TBAB as nucleophilic additive). Colorless oil. ^1H NMR (400 MHz, CDCl_3) δ : 5.86 (tt, J = 53.0 Hz, 4.7 Hz, 1 H),

4.85–4.80 (m, 1 H), 4.50 (t, J = 8.5 Hz, 1 H), 4.36 (dd, J = 8.6 Hz, 5.9 Hz, 1 H), 3.99–3.72 (m, 4 H). ^{13}C NMR (100 MHz, CDCl_3 , δ): 154.7, 114.7 (tt, J = 249.7 Hz, 27.0 Hz), 109.1 (tt, J = 249.6 Hz, 35.4 Hz), 74.6, 71.3, 68.4 (t, J = 28.4 Hz), 65.8. ^{19}F NMR (376 MHz, CDCl_3 , δ): –124.7 (tdt, J = 12.7 Hz, 4.5 Hz, 3.8 Hz, 2 F), –138.9 (dtd, J = 21.9 Hz, 3.8 Hz, 1.9 Hz, 1 F), –139.0 (dtd, J = 22.8 Hz, 3.7 Hz, 1.5 Hz, 1 F). The ^1H NMR spectral data correspond to those in the literature [27], ^{13}C and ^{19}F NMR spectra were not previously presented.

2.6. General procedure for the reaction of epoxides with CS_2

Following the general procedure for the epoxide carboxylation (2.3), a mixture of the epoxide (4 mmol), $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ (0.024 mmol), TBAI (0.064 mmol) and CS_2 (8 mmol) was stirred at 70 or 90 °C (for propylene oxide and styrene oxide, respectively) for 16 h. The reaction yield was determined by NMR.

3. Results and discussion

The reaction of styrene oxide **1a** with CO_2 was used as a model reaction to gauge the activity of different Lewis acids (LA) under the following conditions: 0.6 mol% LA, 1.6 mol% TBAI as nucleophilic additive, 60 °C, 4 atm, neat (Fig. 1). The highest yields were recorded using zinc(II) bromide and chloride. It is known that NbCl_5 can perform well in this reaction [75,76]; however, its catalytic activity (FeCl_3 behaved similarly) was found to be inferior to that of the zinc salts under the above reaction conditions. The lower activity displayed by MgCl_2 (63%) is opposite to the previously shown result, where it was more active than zinc(II) chloride (90% vs. 65%) under the reported conditions [100 °C, 18 h, CO_2 (1 atm), DMF] [35] but could be explained in terms of its poor solubility in the epoxide and the better in DMF as a solvent. Some other Lewis acids tested proved to be less effective catalysts.

Due to the presence in the literature of several examples of the application of unsupported TBAX (tetrabutylammonium halide) [77,78] and other ammonium [79], phosphonium [80,81] and imidazolium [82] salts in the title reaction, TBAI alone was tested in the carboxylation of styrene oxide **1a** but the yield of **2a** did not exceed 30% (Fig. 1).

Next, we explored a variety of inorganic supports for the most active metal salts in order to develop a recyclable catalyst, including silicon, aluminum, titanium and cerium oxides (Fig. 2). The best results were attained with the catalysts based on zinc salts on silica, alumina, titania and ceria as well as on boehmite and calcined Al_2O_3 (89–100%). In contrast, the oxide-supported niobium(V) and iron(III) chlorides showed very moderate activity (50% and 35% yield, respectively), not only lower than the activity of free LA but also comparable with that of the corresponding oxides. It is known that the silicon and aluminum oxides can catalyze themselves the reaction in the presence of a tetrabutylammonium salt [55], that is why their activity was also investigated. It turned out that the application of the SiO_2 -TBAI system gave 60 and 45% yield of **2a** in 16 and 6 h, respectively, the Al_2O_3 -TBAI system gave 45% in 16 h, but the conversion did not exceed 35% in the case of the titanium, zinc and cerium oxides. The results obtained show the phenomenon of a synergetic effect of addition of LA to the oxide, being positive in the case of zinc(II) salts (up to quantitative yield) and negative for NbCl_5 and FeCl_3 (10% decreased yields, from 60% to 50% and from 45% to 35%, respectively). Among the most active catalysts, $\text{ZnCl}_2/\text{SiO}_2$, $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ and $\text{ZnCl}_2/\text{TiO}_2$ allowed to get 100% yields in 6 h, which diminished to 50–74% for a shorter reaction time (2 h).

For further study, $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ was considered the catalyst of choice due to its availability, air stability, low cost and easy application and isolation from the reaction mixture, especially, when compared with $\text{ZnCl}_2/\text{TiO}_2$; the lower impact of Al_2O_3 as catalyst on the reaction yield

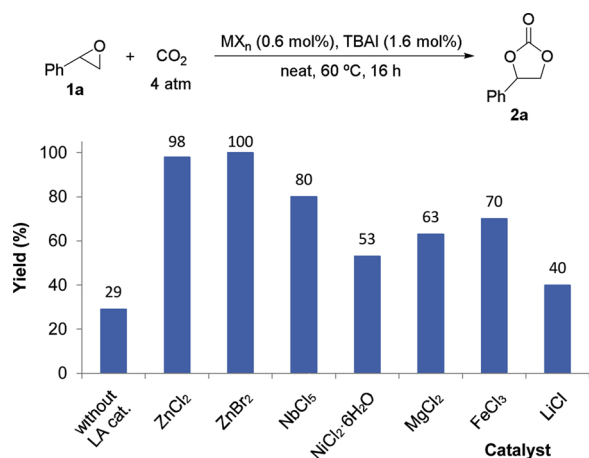


Fig. 1. Screening of Lewis acids (LA) in the synthesis of the cyclic carbonate 2a.

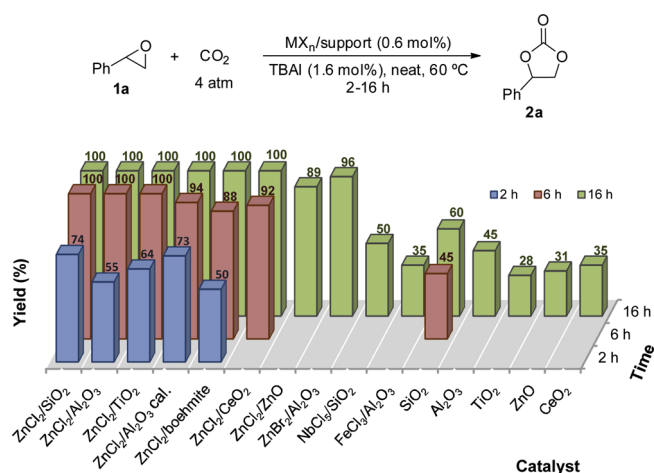


Fig. 2. Screening of supported catalysts and supports in the synthesis of the cyclic carbonate 2a.

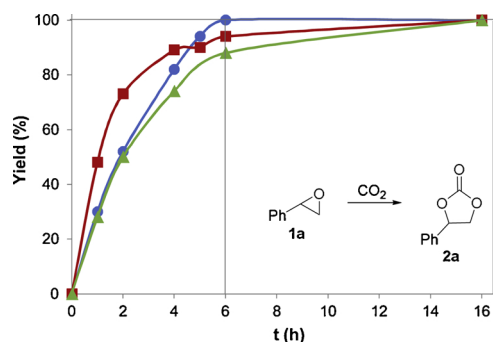


Fig. 3. Kinetic profiles for the synthesis of 2a catalyzed by ZnCl₂/Al₂O₃ (●), ZnCl₂/Al₂O₃calcined (■) and ZnCl₂/boehmite (▲). Reaction conditions: 1a (4.0 mmol), catalyst (0.6 mol%), TBAI (1.6 mol%), neat, 60 °C, 4 atm.

compared to that of SiO₂ was also taken into account. The kinetic data corresponding to the transformation of 1a into 2a, catalyzed by ZnCl₂ on three different alumina supports (Al₂O₃, calcined Al₂O₃ and boehmite), brought into view a higher initial reaction rate for ZnCl₂/Al₂O₃calcined but with a trend to stabilization after 4 h (Fig. 3). Half-conversion was achieved in 2 h with both ZnCl₂/Al₂O₃ and ZnCl₂/boehmite but full conversion was accomplished faster with the former. Such effect could be caused by the difference in morphology of the surface of the supports as well as by the number of hydroxyl groups on

it.

The structural morphology of the catalyst surface and its composition were investigated by scanning electron microscopy (SEM) and energy dispersive X-ray spectroscopy (EDX). SEM images (Fig. 4) before (a) and after (b) the carboxylation process do not show any noticeable changes in the catalyst surface morphology. EDX spectra of these two samples display a close to 2:3:23:33 Cl/Zn/Al/O molar ratio, which corresponds to the structure Zn₃Cl₂Al₂₂O₃₃ and supports the formation of Cl-Zn-O-Al bonds on the surface of alumina.

FT-IR/ATR investigation of the catalyst was performed for its precursors (pure ZnCl₂ and Al₂O₃) and a sample containing larger amount of LA (40 wt%), in order to increase the intensity of the Zn-element signals in the spectra. As shown in Fig. 5, the intensity of the peak at 1410 cm⁻¹ (vw), corresponding to Zn-Cl bond of the catalyst, decreased in comparison with the corresponding slightly shifted peak at 1404 cm⁻¹ (s) of the ZnCl₂ sample. The absorption bands at 1610 cm⁻¹ and 3466 cm⁻¹ correspond to deformation and stretching vibrations of the OH-water groups, respectively, less intensive in the catalyst sample. The decrease of intensity of the Zn-Cl band and appearance of bands at 467, 580, 1069, 1155 and 3279 cm⁻¹, corresponding to Al-Cl, Zn-O and M-OH (M = Zn/Al) groups [83,84] demonstrate the formation of a Cl-Zn-O-Al structure on the surface of the catalyst. The probable structure of the catalyst surface is given in the Fig. 5. It is also supported by previous EXAFS (Extended X-Ray Absorption Fine Structure) analysis on the interaction between ZnCl₂ and the alumina matrix in a rhenium-catalyzed olefin metathesis revealed that Zn was coordinated to both, the surface O and Cl (where Zn/Cl = 1) [85].

The powder XRD patterns (Fig. 6) of ZnCl₂/Al₂O₃ (10 wt%) and Al₂O₃ samples exhibit characteristic peaks of the aluminum oxide support (2θ values of 17.1°, 33.1°, 45.2°, 54.2°, 57.8°, 58.3°, 65.8° and 72.1°). Characteristic peaks of crystalline ZnCl₂ were not observed in the 10 wt% catalyst. The same effect was previously found for silicic (ZnCl₂/SiO₂) catalyst obtained by a similar technique [86]. The PXRD pattern of a ZnCl₂/Al₂O₃ (40 wt%) exhibits characteristic peaks of zinc dichloride (2θ values of 28.9°, 30.0°, 31.0°, 32.6°, 34.5°, 41.1° and 50.9°) and ZnO (2θ values of 32.0°, 34.5°, 36.8°, 49.1° and 57.5°) as well as peak of aluminum hydroxide (2θ value of 18.7°) corresponding to those published before [87,88]. The presence of a large bump distributed in a wide range 10–28° 2θ indicates the presence of an amorphous phase in the catalyst samples, the intensity of which is proportional to the amount of ZnCl₂.

The porous structure of the catalyst and alumina support was determined by BET analysis. As shown in Fig. 7, after ZnCl₂ loading, N₂ adsorption and desorption isotherms have a typical trend, the support's BET surface area slightly decreased from 130 to 116 m²/g, and the pore volume determined at $p/p^0 = 0.99$ was reduced from 0.221 to 0.197 mL/g.

The pore-size distribution curves determined by the BJH method (Fig. 8) for alumina and both samples of the freshly prepared and recovered catalyst show one narrow mode, corresponding to average pore sizes of 6.68 nm for alumina, and 6.45 nm and 6.56 nm for ZnCl₂/Al₂O₃ before and after the reaction, respectively. No pores smaller than 2 nm were observed. The absence of micropores could have a positive effect on the catalytic process, since the rate of the reaction is determined only by the rate of adsorption of reagents by the active catalytic centers, the formation of products and its desorption. The absence of significant changes in the pore distribution (<5%) of the catalyst after the reaction suggests a very promising recycling behavior.

Generally, the synthesis of cyclic carbonates from epoxides proceeds under Lewis acid catalysis in solvent-free media, owing to the fact that the epoxide can serve itself as a solvent at the initial stage and, afterwards, the carbonate generated during the reaction can play this role. The positive effect of carbonates as solvents on the reaction rate was previously described in the literature [89]. We observed that solvents such as methyl ethyl ketone or dioxane gave very modest yields of 2a under the above conditions (Table 1, entries 2 and 3), though the

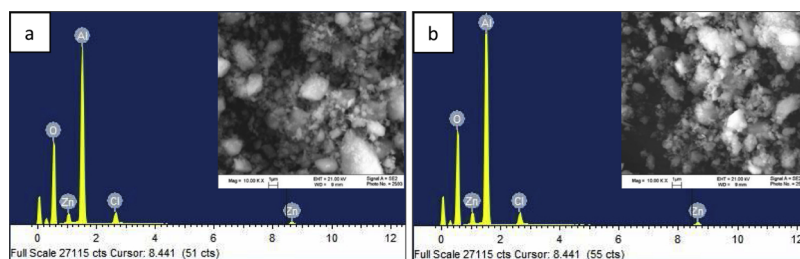


Fig. 4. SEM micrographs and EDX spectra of a $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ sample before (a) and after (b) the reaction.

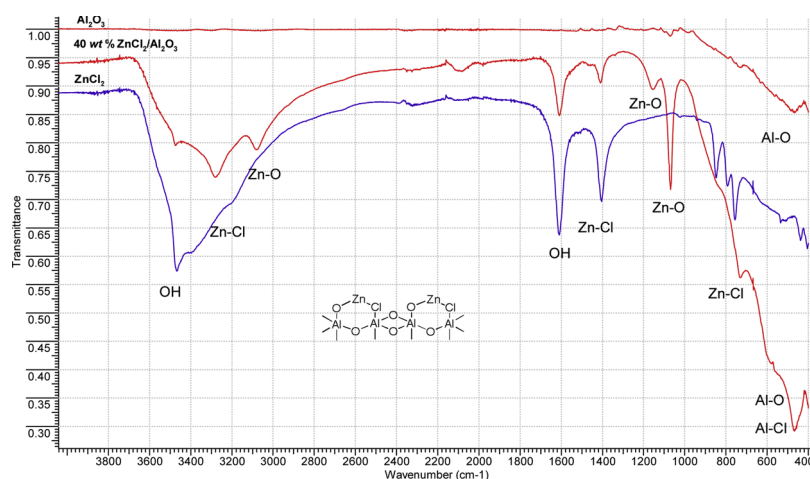


Fig. 5. FT-IR spectra of Al_2O_3 , LA (ZnCl_2) and LA (40 wt%) on alumina support, and probable structure of the catalyst.

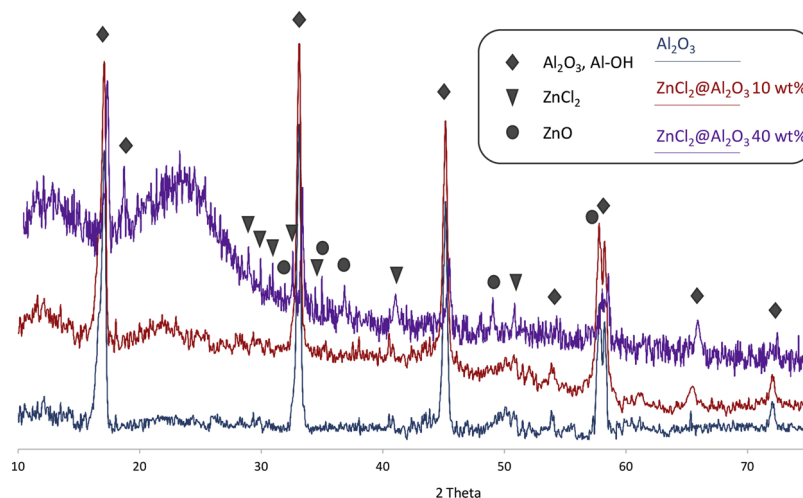


Fig. 6. X-ray diffraction spectrum of the powder samples of Al_2O_3 (blue), ZnCl_2 (10 wt%)/ Al_2O_3 (red) and ZnCl_2 (40 wt%)/ Al_2O_3 (purple) (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article).

deleterious effect on the yield was more dramatic for toluene (Table 1, entry 1). On the contrary, ethylene carbonate as a solvent afforded quantitative yield of **2a** in 16 h (Table 1, entry 5). Gratifyingly, the best result was obtained under solvent-free conditions, with a full conversion being reached in 6 h (Table 1, entry 6).

Then, the activity of ammonium salts as nucleophilic additives was examined. In a control experiment, the necessity for this type of agent was proven to be indispensable (Table 2, entry 1). As it has been mentioned above (Fig. 1), TBAI promotes the reaction by itself but in very poor yield (Table 2, entry 2), though in combination with the Lewis acid, TBAI or TBAB led to nearly quantitative yield when applied

at 1.6 mol% loading for 16 h (Table 2, entries 3 and 4). However, TBAI was found to be superior to TBAB when reducing either the loading or the reaction time (Table 2, entries 5–8), what could be explained by the larger polarizability and leaving group ability of iodide compared to those of bromide. It is noteworthy that the addition of small amounts of TBAI to TBAB (TBAI/TBAB = 0.1–0.3) accelerated the reaction affording 92% yield in 6 h (Table 2, entries 9 and 10). The TBAI/TBAB mixture effect was also evinced in the reaction catalyzed by unsupported zinc(II) chloride (Table 2, entry 11). Therefore, TBAI (1.6 mol%) was chosen as the optimum nucleophilic additive for further investigations, though for the scaling and cheapening of the process the

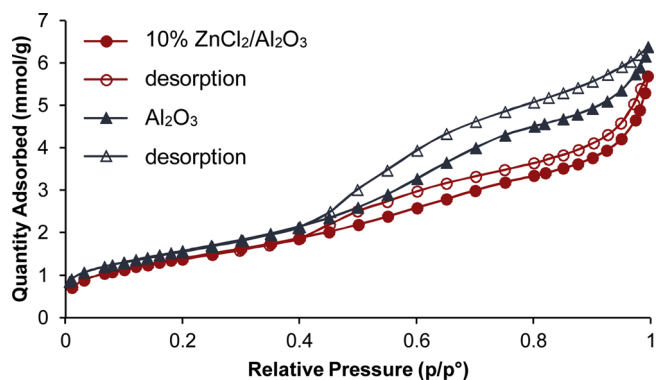


Fig. 7. N₂ adsorption/desorption isotherms of Al₂O₃ (▲/△) and 10 wt% ZnCl₂/Al₂O₃ (●/○).

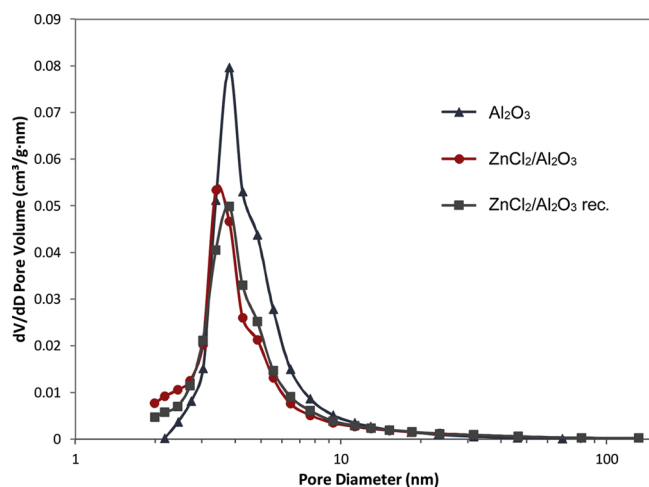


Fig. 8. Pore-size distribution of Al₂O₃ (▲) and ZnCl₂/Al₂O₃ samples before (●) and after (■) styrene oxide (1a) carboxylation.

Table 1
Screening of solvents in the synthesis of 2a.^a

Entry	Solvent	Yield (%) ^a
1	Toluene	<5
2	Dioxane	33
3	Methyl ethyl ketone	44
4	Ethylene carbonate	100
5	Neat	100
6	Neat	100 ^b

^a Yield determined by NMR based on 1a.

^b 6 h.

combination of TBAB and TBAI looks more promising.

The influence of the temperature and CO₂ pressure on the carboxylation of 1a was also assessed for a reaction time of 2 h (Fig. 9). The yield upgrade experienced when increasing either the temperature or the pressure was previously pointed up in the synthesis of cyclic carbonates [74]. The same trend was recorded in our case: the product yield rose from 39% at 40 °C to 55% at 60 °C, and to 79% at 80 °C; every 2 atm increment of the CO₂ pressure increased the yield in 6–15%. The reaction carried out under the mildest conditions (rt, 1 atm. CO₂) was significantly slowed down and gave 82% yield in 24 h.

The optimal conditions (60 °C, 4 atm, CO₂), efficient and quite mild

and economic, were applied to the aromatic and aliphatic epoxides styrene (1a) and propylene (1b) oxides, respectively, in order to compare their kinetic profiles (Fig. 10). Both cyclic carbonates (2a and 2b) were formed in quantitative yield but the rate of formation of 2b was considerably higher than that of 2a. This behavior could be explained, in part, by steric effects, as previously observed in the reaction of epoxides bearing bulky substituents catalyzed by sterically hindered aluminum complexes [90] or heterogeneous catalysts [91]. However, electronic effects can play a more dominant role because of the better delocalization of the negative charge on the styrene-derived alkoxide intermediate, which reduces its nucleophilic character and, subsequently, attenuates the reaction of the alkoxide with CO₂ and, in turn, the reaction rate [92].

We extended the optimized conditions to a range of differently substituted oxiranes (Table 3). Both styrene oxide (1a) and propylene oxide (1b) were quantitatively transformed into the corresponding cyclic carbonates 2a and 2b irrespective of using alumina or titania as supports; as pointed out above, 1b reacted faster than 1a even at a pressure of 2 atm. An increase in the length of the alkyl chain, as in 2-hexyloxirane (1c), made the reaction slower when compared with propylene oxide (1b). The reaction conditions were compatible with the presence of a carbon-carbon double bond (1d) or chlorine atom (1e) in the starting epoxide; a possible chloro-iodo exchange in 2e was not detected. The yield of the chloroaromatic carbonate 2f was substantially improved just by increasing the reaction time from 6 to 8 h. Quantitative yields were also noted for epoxides 2g and 2h, albeit higher temperature or longer reaction time were necessary, with the presence of ethylene carbonate preventing solidification of the reaction mixture because of the high-melting of the products 2g and 2h.

It is known that disubstituted epoxides are more reluctant to react with CO₂ than the monosubstituted counterparts, especially when they have a bicyclic structure [35,44,46]. For instance, 1,1-dimethyloxirane (1i) gave the expected carbonate 2i in moderate yield after 16 h. The carboxylation of the cyclic epoxides 1j and 1k was better effected with the more active ZnBr₂/Al₂O₃ catalyst under harsher conditions (8 atm, 80 °C) and double catalyst loading (1.2 mol% for 1k). At any rate, their conversion was incomplete leading to the *cis* bicyclic carbonates 2j and 2k in 76% and 39% yield, respectively.

Fluorinated carbonates are used as electrolytic additives in Li-ion [93,94] and Na-ion [95] batteries for increasing capacity, oxidation resistance and incombustibility. The simplest route to this type of compounds is the direct fluorination [96], though it results in a mixture of products because of the lack of selectivity. Our proposed carboxylation of the fluorinated epoxides 1l–n provided the desired carbonates under moderate temperature and pressure (70 °C, 6 atm). Moreover, the use of the less active TBAB instead of TBAI was also efficient. It is worthy of note that the cyclic carbonates 2l–m are new polyfluorinated products and were obtained in quantitative yields with 100% selectivity.

The recyclability of the catalyst was examined in the carboxylation of propylene oxide (1b) as the most reactive substrate (Fig. 11). The catalytic system ZnCl₂/Al₂O₃-TBAI could be reused, at least, five times without loss of activity. Recycling tests with incomplete conversion (75% in 20 min) of 1a were successfully carried out and no drop in activity upon catalyst recycling was observed. Interestingly, not only ZnCl₂/Al₂O₃ could be recovered by centrifugation from the reaction crude, but up to 80% of the amount of TBAI was also recycled by precipitation from the centrifuged mixture with diethyl ether, and added to a new loading of reagents.

When compared with other catalytic systems, ZnCl₂/Al₂O₃-TBAI is readily available, active under quite mild conditions [55,57–60,64–70] and recyclable. Moreover, it works in the absence of ligands [23,39,40,47,48] with an activity not inferior to that of other heterogeneous catalysts [55,57–66,68,65–70].

A reaction mechanism for the catalytic carboxylation of epoxides on the ZnCl₂/Al₂O₃ surface was put forward (Scheme 1). First, it seems

Table 2
Screening of nucleophilic additives in the synthesis of **2a**.

$\text{Ph-epoxide } \mathbf{1a} + \text{CO}_2 \xrightarrow[\text{co-catalyst, neat, 60 } ^\circ\text{C}]{\text{ZnCl}_2/\text{Al}_2\text{O}_3 \text{ (0.6 mol\%)}} \text{Ph-carboxylate } \mathbf{2a}$			
Entry	Additive (mol%)	Time (h)	Yield (%) ^a
1	–	16	<1
2	TBAI (1.6)	16	29 ^b
3	TBAI (1.6)	16	100
4	TBAB (1.6)	16	97
5	TBAI (0.2)	6	38
6	TBAI (0.6)	6	74
7	TBAI (1.6)	6	100
8	TBAB (1.6)	6	70
9	TBAB (1.2) + TBAI (0.4)	6	92
10	TBAB (1.44) + TBAI (0.16)	6	91
11	TBAB (1.44) + TBAI (0.16)	6	92 ^c

^a Yield determined by NMR based on **1a**.

^b Without Lewis acid catalyst.

^c Unsupported ZnCl₂ as catalyst.

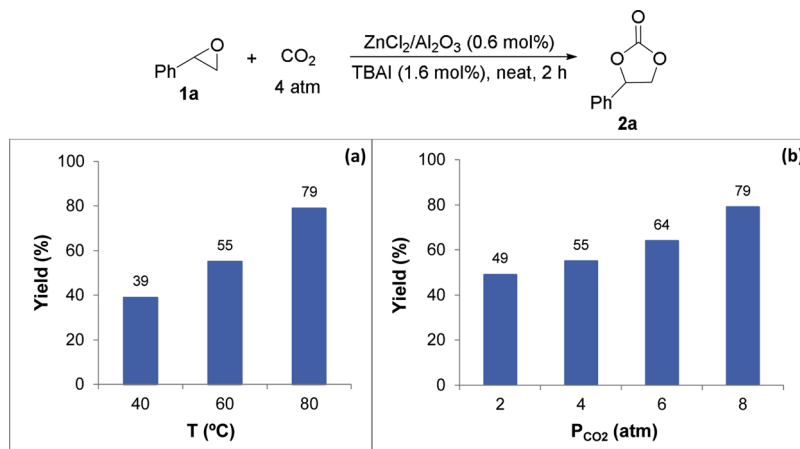


Fig. 9. Study of the effect of (a) the temperature (P_{CO2} = 4 atm) and (b) the CO₂ pressure (T = 60 °C) on the yield of the carboxylation of epoxide **1a**.











































Fig. 10. Kinetic profiles for the carboxylation of styrene (**1a**, ♦) and propylene (**1b**, ■) catalyzed by ZnCl₂/Al₂O₃-TBAI. Reaction conditions: **1a** (4.0 mmol), catalyst (0.6 mol%), TBAI (1.6 mol%), neat, 60 °C, 4 atm.

reasonable to suggest that Zn could activate both CO₂ [92,97,98] and the epoxide [92] by intensifying their electrophilicity. The coordination of Zn on the surface of Al₂O₃ to the epoxide is also supported by the appearance in the FT-IR spectrum of the broad intense bands (at 1132 cm⁻¹ and 1157 cm⁻¹), probably attributed to the stretching modes of Zn–O–C group along with the characteristic C–O–C band of epoxide

ring at 1259 cm⁻¹ (See ESI for spectra). Iodide ion attack on the terminal or internal oxirane carbon of the alkyl or aryl-substituted epoxides [99–101], respectively, would furnish the alkoxide species ready to add to CO₂. Intramolecular 5-*exo-tet* cyclization of the acyclic mixed carbonate would release the cyclic carbonate and iodide ion, with the latter entering the catalytic cycle again.

Carbon disulfide is an easily available and inexpensive building block for organic synthesis, widely used in the chemical industry. Although CS₂ is an isoelectronic heterocumulene of carbon dioxide, its reaction with epoxides has been much less explored. The reaction results, in most cases, in a mixture of the 1,3-oxathiolane-2-thione and 1,3-dithiolane-2-thione as well as in 1,3-dithiolane-2-ones, 1,3-oxathiolane-2-ones, 1,3-dioxolane-2-thiones and thiiranes [102–104]; therefore, good functional group selectivity is the most important goal to achieve in this process. The same catalytic system optimized for the carboxylation of epoxides was tested in the thiocarboxylation variant with a minimum amount of CS₂. Propylene oxide (**1b**) reacted with full conversion at 70 °C for 16 h producing a mixture of the propylene di- and trithiocarbonates **3b** and **4b** (57% and 27% yield, respectively). In contrast, the reaction of styrene oxide (**1a**) with CS₂ was far more selective, giving rise to styrene trithiocarbonate **4a** in 61% yield at 90 °C (Scheme 2).

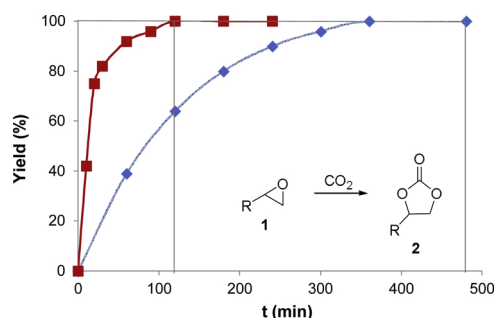Table 3
Reaction of epoxides **1** with CO₂^a.

$\text{R} \begin{array}{c} \diagup \text{O} \diagdown \\ \text{---} \end{array} + \text{CO}_2 \xrightarrow[\text{TBAI (1.6 mol\%, neat, 4 atm)}]{\text{ZnCl}_2/\text{support (0.6 mol\%)}} \text{R} \begin{array}{c} \diagup \text{O} \diagdown \\ \text{---} \end{array} \text{O} \begin{array}{c} \diagup \text{O} \diagdown \\ \text{---} \end{array}$						
Epoxide	Catalyst	T (°C)	t (h)	Product	Yield (%) ^b	TON/TOF ^c
 1a	ZnCl ₂ /Al ₂ O ₃	60	6		100	167/28
	ZnCl ₂ /TiO ₂	60	6		100	— nd
 1b	ZnCl ₂ /Al ₂ O ₃	60	2		100	167/83
	ZnCl ₂ /TiO ₂	60	2		100	833 ^d /417 ^d
	ZnCl ₂ /Al ₂ O ₃	60	2		97 ^e	— nd
 1c	ZnCl ₂ /Al ₂ O ₃	60	16		100	167/10
		60	6		98	163/27
 1d	ZnCl ₂ /Al ₂ O ₃	60	6		100	167/28
 1e	ZnCl ₂ /Al ₂ O ₃	60	6		87	145/24
 1f	ZnCl ₂ /Al ₂ O ₃	60	6		80	133/22
		60	8		96	160/20
 1g	ZnCl ₂ /Al ₂ O ₃	60	3		70	— nd
		100	4		100	167/42
		60	16		100 ^f	— nd
 1h	ZnCl ₂ /Al ₂ O ₃	100	4		100 ^f	167/42
 1i	ZnCl ₂ /Al ₂ O ₃	60	16		61	102/6
 1j	ZnCl ₂ /Al ₂ O ₃	60	16		11 ^g	— nd
		100	16		34 ^g	57/4
		110	32		60 ^h	100/3
	ZnBr ₂ /Al ₂ O ₃	60	16		21 ^g	— nd
		80	24		76 ⁱ	127/5
 1k	ZnBr ₂ /Al ₂ O ₃	80	16		39 ⁱ	33/2
 1l	ZnCl ₂ /Al ₂ O ₃	70	24		100 ^{h,j}	167/7
 1m	ZnCl ₂ /Al ₂ O ₃	70	24		100 ^{h,j}	167/7
 1n	ZnCl ₂ /Al ₂ O ₃	70	24		100 ^{h,j}	167/7

^a Reaction conditions: **1** (4.0 mmol), catalyst (0.6 mol%), TBAI (1.6 mol%), neat, 4 atm.

^b Isolated yield.

^c TON (turnover number: mmol_{product}/mmol_{catalyst}) and TOF (turnover frequency: mmol_{product}/(mmol_{catalyst}·time), h⁻¹) were determined under optimal conditions for each substrate.

^d TON or TOF in 5 cycles.

^e 2 atm.

^f In ethylene carbonate.

^g Yield determined by NMR.

^h 6 atm.

ⁱ 8 atm.

^j TBAB.



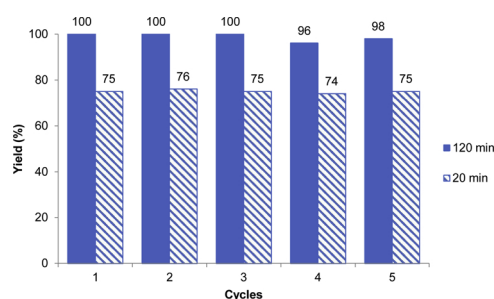


Fig. 11. Recycling of $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ in the synthesis of propylene carbonate **2b**. Reaction conditions: **1b** (4.0 mmol), $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ (0.6 mol%), TBAI (1.6 mol%), 60 °C, 4 atm, 2 h (■) or 20 min (▨).

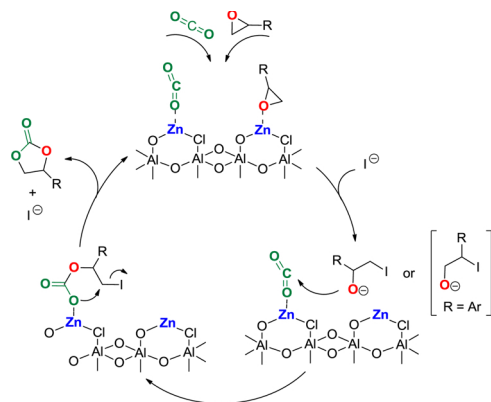

Scheme 1. Reaction mechanism proposed for epoxide carboxylation catalyzed by $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ -TBAI.



Scheme 2. Reaction of epoxides **1a** and **1b** with CS_2 catalyzed by $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ -TBAI.

4. Conclusions

The results of this study suggest a new avenue for research on epoxide carboxylation based on heterogeneous catalysis: the first heterogeneous ZnCl_2 -catalyzed carboxylation of epoxides in the presence of a tetrabutylammonium halide has been presented. A thorough comparison of the activity of different Lewis acids and their supports led to the conclusion that $\text{ZnCl}_2/\text{Al}_2\text{O}_3$ was the catalyst of choice for the title reaction because of being efficient, cheap and easily prepared and applied. When combined with tetrabutylammonium iodide as nucleophilic additive, the obtained catalytic system has allowed to perform the reaction under relatively mild (typically, 60 °C, 4 atm) and solvent-free conditions. Most of the monosubstituted carbonates have been synthesized in quantitative yields, including novel polyfluorinated ones, whereas disubstituted epoxides were more averse to react. The activity at low catalyst loading (0.6 mol% ZnCl_2 , 1.6 mol% TBAI) is comparable or superior (in some cases) to that of other more complex heterogeneous catalysts or homogeneous aluminum complexes. Both, the catalyst ($\text{ZnCl}_2/\text{Al}_2\text{O}_3$) and the quaternary ammonium salt (TBAI) have been easily recovered and successfully reused in five cycles with no loss of activity. This fact, together with the small amounts of zinc and ammonium salts deployed, the solvent-free medium and the moderate temperature and pressure employed, makes the process economically and ecologically attractive and sustainable. Furthermore, the aforementioned catalytic system has been shown to be also effective in

the reaction of epoxides with carbon disulfide to form di- or trithio-carbonates.

Acknowledgments

This study was generously supported by the Russian Science Foundation [project no. 14-23-00186 P], the M. V. Lomonosov Moscow State University Program of Development, the Spanish Ministerio de Ciencia, Innovación y Universidades [MICIU; grant no. CTQ2017-88171-P] and the Generalitat Valenciana [GV; grant no. AICO/2017/007].

Appendix A. Supplementary data

Supplementary material related to this article can be found, in the online version, at doi:<https://doi.org/10.1016/j.apcatb.2019.04.024>.

References

- [1] M. Aresta, A. Dibenedetto, A. Angelini, Catalysis for the valorization of exhaust carbon: from CO_2 to chemicals, materials, and fuels. *Technological use of CO_2* , *Chem. Rev.* 114 (2014) 1709–1742 Review.
- [2] T. Sakakura, J.C. Choi, H. Yasuda, Transformation of carbon dioxide, *Chem. Rev.* 107 (2007) 2365–2387 Review.
- [3] I. Omae, Recent developments in carbon dioxide utilization for the production of organic chemicals, *Coord. Chem. Rev.* 256 (2012) 1384–1405 Review.
- [4] Q. Liu, L. Wu, R. Jackstell, M. Beller, Using carbon dioxide as a building block in organic synthesis, *Nat. Commun.* 6 (5933) (2015) 1–15 Review.
- [5] Q.-W. Song, Z.-H. Zhou, L.-N. He, Efficient, selective and sustainable catalysis of carbon dioxide, *Green Chem.* 19 (2017) 3707–3728 Review.
- [6] C. Martín, G. Fiorani, A.W. Kleij, Recent advances in the catalytic preparation of cyclic organic carbonates, *ACS Catal.* 5 (2015) 1353–1370 Review.
- [7] R.R. Shaikh, S. Pornpraprom, V. D'Elia, Catalytic strategies for the cycloaddition of pure, diluted, and waste CO_2 to epoxides under ambient conditions, *ACS Catal.* 8 (2018) 419–450 Review.
- [8] M.A. Pacheco, C.L. Marshall, Review of dimethyl carbonate (DMC) manufacture and its characteristics as a fuel additive, *Energy Fuels* 11 (1997) 2–29 Review.
- [9] M.O. Sonnati, S. Amigoni, E.P. Taffin de Givenchy, T. Darmanin, O. Choulet, F. Guittard, Glycerol carbonate as a versatile building block for tomorrow: synthesis, reactivity, properties and applications, *Green Chem.* 15 (2013) 283–306 Review.
- [10] S.J. Poland, D.J. Darensbourg, A quest for polycarbonates provided via sustainable epoxide/ CO_2 copolymerization processes, *Green Chem.* 19 (2017) 4990–5011 Review.
- [11] B. Schöffner, F. Schöffner, S.P. Verevkin, A. Börner, Organic carbonates as solvents in synthesis and catalysis, *Chem. Rev.* 110 (2010) 4554–4581 Review.
- [12] Q. Li, J. Chen, L. Fan, X. Kong, Y. Lu, Progress in electrolytes for rechargeable Li-based batteries and beyond, *Green Energy Environ.* 1 (2016) 18–42 Review.
- [13] J. Vaitla, Y. Guttormsen, J.K. Mannisto, A. Nova, T. Repo, A. Bayer, K.H. Hopmann, Enantioselective incorporation of CO_2 : status and potential, *ACS Catal.* 7 (2017) 7231–7244 Perspective.
- [14] W. Guo, J.E. Gómez, À. Cristófol, J. Xie, A.W. Kleij, Catalytic transformations of functionalized cyclic organic carbonates, *Angew. Chem. Int. Ed.* 57 (2018) 13735–13747 Minireview.
- [15] S. Foltran, R. Mereau, T. Tassaing, Theoretical study on the chemical fixation of carbon dioxide with propylene oxide catalyzed by ammonium and guanidinium salts, *Catal. Sci. Technol.* 4 (2014) 1585–1597.
- [16] C. Maeda, Y. Miyazaki, T. Ema, Recent progress in catalytic conversions of carbon dioxide, *Catal. Sci. Technol.* 4 (2014) 1482–1497 Perspective.
- [17] C.J. Whiteoak, A.W. Kleij, Development in the context of ring expansion–addition of carbon dioxide to epoxides to give organic carbonates, *Synlett* 24 (2013) 1748–1756. Account.
- [18] M. Cokoja, M.E. Wilhelm, M.H. Anthofer, W.A. Herrmann, F.E. Kühn, Synthesis of cyclic carbonates from epoxides and carbon dioxide by using organocatalysts, *ChemSusChem* 8 (2015) 2436–2454 Review.
- [19] V. D'Elia, J.D.A. Pelletier, J.-M. Basset, Cycloadditions to epoxides catalyzed by group III–V transition-metal complexes, *ChemCatChem* 7 (2015) 1906–1917 Minireview.
- [20] J. Meléndez, M. North, R. Pasquale, Synthesis of cyclic carbonates from atmospheric pressure carbon dioxide using exceptionally active aluminium(salen) complexes as catalysts, *Eur. J. Inorg. Chem.* (2007) 3323–3326.
- [21] W. Clegg, R.W. Harrington, M. North, R. Pasquale, Cyclic carbonate synthesis catalysed by bimetallic aluminium–salen complexes, *Chem. Eur. J.* 16 (2010) 6828–6843.
- [22] J.A. Castro-Osma, M. North, X. Wu, Synthesis of cyclic carbonates catalysed by chromium and aluminium salphen complexes, *Chem. Eur. J.* 22 (2016) 2100–2107.
- [23] X. Wu, M. North, A bimetallic aluminium(salphen) complex for the synthesis of cyclic carbonates from epoxides and carbon dioxide, *ChemSusChem* 10 (2017) 74–78.

- [24] J. Melendez, M. North, P. Villuendas, C. Young, One-component bimetallic aluminum(salen)-based catalysts for cyclic carbonate synthesis and their immobilization, *Dalton Trans.* 40 (2011) 3885–3902.
- [25] Y. Xu, D. Yuan, Y. Wang, Y. Yao, Aluminum complexes derived from a hexadentate salen-type Schiff base: synthesis, structure, and catalysis for cyclic carbonate synthesis, *Dalton Trans.* 46 (2017) 5848–5855.
- [26] J. Steinbauer, T. Werner, Poly(ethylene glycol)s as ligands in calcium-catalyzed cyclic carbonate synthesis, *ChemSusChem* 10 (2017) 3025–3029.
- [27] J. Steinbauer, A. Spannenberg, T. Werner, An in situ formed Ca^{2+} -crown ether complex and its use in CO_2 -fixation reactions with terminal and internal epoxides, *Green Chem.* 19 (2017) 3769–3779.
- [28] L. Longwitz, J. Steinbauer, A. Spannenberg, T. Werner, Calcium-based catalytic system for the synthesis of bio-derived cyclic carbonates under mild conditions, *ACS Catal.* 8 (2018) 665–672.
- [29] C.-Y. Li, Y.-C. Su, C.-H. Lin, H.-Y. Huang, C.-Y. Tsai, T.-Y. Lee, B.-T. Ko, Synthesis and characterization of trimetallic cobalt, zinc and nickel complexes containing amine-bis(benzotriazole phenolate) ligands: efficient catalysts for coupling of carbon dioxide with epoxides, *Dalton Trans.* 46 (2017) 15399–15406.
- [30] C.J. Whiteoak, N. Kiehl, V. Laserna, E.C. Escudero-Adán, E. Martin, A.W. Kleij, A powerful aluminum catalyst for the synthesis of highly functional organic carbonates, *J. Am. Chem. Soc.* 135 (2013) 1228–1231.
- [31] Y. Qin, H. Guo, X. Sheng, X. Wang, F. Wang, An aluminum porphyrin complex with high activity and selectivity for cyclic carbonate synthesis, *Green Chem.* 17 (2015) 2853–2858.
- [32] Y. Yang, C.-Y. Gao, H.-R. Tian, J. Ai, X. Min, Z.-M. Sun, A highly stable Mn^{II} phosphonate as a highly efficient catalyst for CO_2 fixation under ambient conditions, *Chem. Commun.* 54 (2018) 1758–1761.
- [33] C. Xu, Y. Liu, L. Wang, J. Ma, L. Yang, F.-X. Pan, A.M. Kirillov, W. Liu, New lanthanide(III) coordination polymers: synthesis, structural features, and catalytic activity in CO_2 fixation, *Dalton Trans.* 46 (2017) 16426–16431.
- [34] J. Martinez, J. Fernandez-Baeza, L.F. Sanchez-Barba, J.A. Castro-Osma, A. Lara-Sanchez, A. Otero, An efficient and versatile lanthanum heteroscorpionate catalyst for carbon dioxide fixation into cyclic carbonates, *ChemSusChem* 10 (2017) 2886–2890.
- [35] T. Fujihara, M. Inokuchi, T. Mizoe, K. Nogi, J. Terao, Y. Tsuji, Synthesis of cyclic carbonates from epoxides and carbon dioxide catalyzed by MgCl_2 , *Chem. Lett.* 46 (2017) 968–969.
- [36] H. Kisch, R. Millini, I.-J. Wang, Bifunktionelle katalysatoren zur synthese cyclischer carbonate aus oxiranen und kohlendioxid, *Chem. Ber.* 119 (1986) 1090–1094.
- [37] A. Decortes, M. Martinez Belmonte, J. Benet-Buchholz, A.W. Kleij, Efficient carbonate synthesis under mild conditions through cycloaddition of carbon dioxide to oxiranes using a Zn(salphen) catalyst, *Chem. Commun.* 46 (2010) 4580–4582.
- [38] A. Decortes, A.W. Kleij, Ambient fixation of carbon dioxide using a Zn^{II} salphen catalyst, *ChemCatChem* 3 (2011) 831–834.
- [39] S. He, F. Wang, W.-L. Tong, S.-M. Yiu, M.C.W. Chan, Topologically diverse shape-persistent bis-(Zn-salphen) catalysts: efficient cyclic carbonate formation under mild conditions, *Chem. Commun.* 52 (2016) 1017–1020.
- [40] B. Bousquet, A. Martinez, V. Dufaud, Zinc-azatrane complexes as efficient catalysts for the conversion of carbon dioxide into cyclic carbonates, *ChemCatChem* 10 (2018) 843–848.
- [41] E. Mercade, E. Zangrando, C. Claver, C. Godard, Robust zinc complexes that contain pyrrolidine-based ligands as recyclable catalysts for the synthesis of cyclic carbonates from carbon dioxide and epoxides, *ChemCatChem* 8 (2016) 234–243.
- [42] P. Patel, B. Parmar, R.I. Kureshy, N.H. Khan, E. Suresh, Efficient solvent free CO_2 fixation reactions with epoxides under mild conditions by mixed ligand Zn(II) MOFs, *ChemCatChem* 10 (2018) 2401–2408.
- [43] C.-S. Cao, Y. Shi, H. Xu, B. Zhao, A multifunctional MOF as a recyclable catalyst for the fixation of CO_2 with aziridines or epoxides and as a luminescent probe of Cr(VI), *Dalton Trans.* 47 (2018) 4545–4553.
- [44] W. Cheng, Z. Fu, J. Wang, J. Sun, S. Zhang, ZnBr_2 -based choline chloride ionic liquid for efficient fixation of CO_2 to cyclic carbonate, *Synth. Commun.* 42 (2012) 2564–2573.
- [45] H. Zhang, X. Kong, C. Cao, G. Pang, Y. Shi, An efficient ternary catalyst $\text{ZnBr}_2/\text{K}_2\text{CO}_3/[\text{bmim}]\text{Br}$ for chemical fixation of CO_2 into cyclic carbonates at ambient conditions, *J. CO₂ Util.* 14 (2016) 76–82.
- [46] C. Maeda, J. Shimomishi, R. Miyazaki, J. Hasegawa, T. Ema, Highly active and robust metalloporphyrin catalysts for the synthesis of cyclic carbonates from a broad range of epoxides and carbon dioxide, *Chem. Eur. J.* 22 (2016) 6556–6563.
- [47] C. Maeda, S. Sasaki, T. Ema, Electronic tuning of zinc porphyrin catalysts for the conversion of epoxides and carbon dioxide into cyclic carbonates, *ChemCatChem* 9 (2017) 946–949.
- [48] C. Maeda, T. Taniguchi, K. Ogawa, T. Ema, Bifunctional catalysts based on *m*-phenylene-bridged porphyrin dimer and trimer platforms: synthesis of cyclic carbonates from carbon dioxide and epoxides, *Angew. Chem. Int. Ed.* 54 (2015) 134–138.
- [49] Y. Yang, Y. Hayashi, Y. Fujii, T. Nagano, Y. Kita, T. Ohshima, J. Okuda, K. Mashima, Efficient cyclic carbonate synthesis catalyzed by zinc cluster systems under mild conditions, *Catal. Sci. Technol.* 2 (2012) 509–513.
- [50] L. Yang, H. Wang, Recent advances in carbon dioxide capture, fixation, and activation by using *N*-heterocyclic carbenes, *ChemSusChem* 7 (2014) 962–998 Review.
- [51] X. Liu, C. Ciao, Y. Li, P. Guan, L. Yang, Y. Shi, Cycloaddition of CO_2 to epoxides catalyzed by *N*-heterocyclic carbene (NHC)– ZnBr_2 system under mild conditions, *Synlett* 23 (2012) 1343–1348.
- [52] L. Martínez-Rodríguez, J. Ojalora Garmilla, A.W. Kleij, Cavitand-based polyphenols as highly reactive organocatalysts for the coupling of carbon dioxide and oxiranes, *ChemSusChem* 9 (2016) 749–755.
- [53] S. Sopena, E. Martin, E.C. Escudero-Adán, A.W. Kleij, Pushing the limits with squaramide-based organocatalysts in cyclic carbonate synthesis, *ACS Catal.* 7 (2017) 3532–3539.
- [54] C. Descorme, P. Gallezot, C. Geantet, C. George, Heterogeneous catalysis: a key tool toward sustainability, *ChemCatChem* 4 (2012) 1897–1906 Review.
- [55] T. Cao, L. Sun, Y. Shi, L. Hua, R. Zhang, L. Guo, W. Zhu, Z. Hou, The role of inorganic oxide supports in synthesis of cyclic carbonates from carbon dioxide and epoxides, *Chin. J. Catal.* 33 (2012) 416–424.
- [56] B.-H. Xu, J.-Q. Wang, J. Sun, Y. Huang, J.-P. Zhang, X.-P. Zhang, S.-J. Zhang, Fixation of CO_2 into cyclic carbonates catalyzed by ionic liquids: a multi-scale approach, *Green Chem.* 17 (2015) 108–122 Review.
- [57] W.-L. Dai, L. Chen, S.-F. Yin, W.-H. Li, Y.-Y. Zhang, S.-L. Luo, C.-T. Au, High-efficiency synthesis of cyclic carbonates from epoxides and CO_2 over hydroxyl ionic liquid catalyst grafted onto cross-linked polymer, *Catal. Lett.* 137 (2010) 74–80.
- [58] H. Xie, H. Duan, S. Li, S. Zhang, The effective synthesis of propylene carbonate catalyzed by silica-supported hexaalkylguanidinium chloride, *New J. Chem.* 29 (2005) 1199–1203.
- [59] F.D. Bobbink, A.P. Van Muyden, A. Gopakumar, Z. Fei, P.J. Dyson, Synthesis of cross-linked ionic poly(styrenes) and their application as catalysts for the synthesis of carbonates from CO_2 and epoxides, *ChemPlusChem* 82 (2017) 144–151.
- [60] W. Zhong, F.D. Bobbink, Z. Fei, P.J. Dyson, Polyimidazolium salts: robust catalysts for the cycloaddition of carbon dioxide into carbonates in solvent-free conditions, *ChemSusChem* 10 (2017) 2728–2735.
- [61] M.V. Zakharova, F. Kleitz, F.-G. Fontaine, Carbon dioxide oversolubility in nano-confined liquids for the synthesis of cyclic carbonates, *ChemCatChem* 9 (2017) 1886–1890.
- [62] C.K. Karan, M.C. Sau, M. Bhattacharjee, A copper(II) metal-organic hydrogel as a multifunctional pre-catalyst for CuAAC reactions and chemical fixation of CO_2 under solvent free conditions, *Chem. Commun.* 53 (2017) 1526–1529.
- [63] L. Liu, S.-M. Wang, Z.-B. Han, M. Ding, D.-Q. Yuan, H.-L. Jiang, Exceptionally robust indium based metal-organic framework for highly efficient carbon dioxide capture and conversion, *Inorg. Chem.* 55 (2016) 3558–3565.
- [64] J. Ai, X. Min, C.-Y. Gao, H.-R. Tian, S. Dang, Z.-M. Sun, A copper-phosphonate network as a high performance heterogeneous catalyst for the CO_2 cycloaddition reactions and alcoholysis of epoxides, *Dalton Trans.* 46 (2017) 6756–6761.
- [65] V.B. Saptal, B. Nanda, K.M. Parida, B.M. Bhanage, Fabrication of amine and zirconia on MCM-41 as acid-base catalysts for the fixation of carbon dioxide, *ChemCatChem* 9 (2017) 4105–4111.
- [66] J. Xiong, R.-X. Yang, Y. Xie, N.-Y. Huang, K. Zou, W.-Q. Deng, Formation of cyclic carbonates from CO_2 and epoxides catalyzed by a cobalt-coordinated conjugated microporous polymer, *ChemCatChem* 9 (2017) 2584–2587.
- [67] G.P. Ji, Z. Yang, H. Zhang, Y. Zhao, B. Yu, Z. Ma, Z.M. Liu, Hierarchically mesoporous *o*-hydroxyazobenzene polymers: synthesis and their applications in CO_2 capture and conversion, *Angew. Chem. Int. Ed.* 55 (2016) 9685–9689.
- [68] K.M. Bhin, J. Tharun, K.R. Roshan, D.-W. Kim, Y. Chung, D.-W. Park, Catalytic performance of zeolitic imidazolate framework ZIF-95 for the solventless synthesis of cyclic carbonates from CO_2 and epoxides, *J. CO₂ Util.* 17 (2017) 112–118.
- [69] J. Peng, H.-J. Yang, Y. Geng, Z. Wei, L. Wang, C.-Y. Guo, Novel, recyclable supramolecular metal complexes for the synthesis of cyclic carbonates from epoxides and CO_2 under solvent-free conditions, *J. CO₂ Util.* 17 (2017) 243–255.
- [70] W.-L. Dai, S.-F. Yin, R. Guo, S.-L. Luo, X. Du, C.-T. Au, Synthesis of propylene carbonate from carbon dioxide and propylene oxide using Zn-Mg-Al composite oxide as high-efficiency catalyst, *Catal. Lett.* 136 (2010) 35–44.
- [71] J.W. Comerford, I.D.V. Ingram, M. North, X. Wu, Sustainable metal-based catalysts for the synthesis of cyclic carbonates containing five-membered rings, *Green Chem.* 17 (2015) 1966–1987 Review.
- [72] A. Pinaka, G.C. Vougioukalakis, Using sustainable metals to carry out “green” transformations: Fe- and Cu-catalyzed CO_2 monetization, *Coord. Chem. Rev.* 288 (2015) 69–97 Review.
- [73] : Qing He, J.W. O'Brien, K.A. Kitselman, L.E. Tompkins, G.C.T. Curtis, F.M. Kerton, Synthesis of cyclic carbonates from CO_2 and epoxides using ionic liquids and related catalysts including choline chloride-metal halide mixtures, *Catal. Sci. Technol.* 4 (2014) 1513–1528 Review.
- [74] X.-D. Lang, L.-N. He, Green catalytic process for cyclic carbonate synthesis from carbon dioxide under mild conditions, *Chem. Rec.* 16 (2016) 1337–1352 Review.
- [75] A. Monassier, V. D'Elia, M. Cokoja, H. Dong, J.D.A. Pelletier, J.-M. Basset, F.E. Kuhn, Synthesis of cyclic carbonates from epoxides and CO_2 under mild conditions using a simple, highly efficient niobium-based catalyst, *ChemCatChem* 5 (2013) 1321–1324.
- [76] M.E. Wilhelm, M.H. Anthofer, R.M. Reich, V. D'Elia, J.-M. Basset, W.A. Herrmann, M. Cokoja, F.E. Kuhn, Niobium(V) chloride and imidazolium bromides as efficient dual catalyst systems for the cycloaddition of carbon dioxide and propylene oxide, *Catal. Sci. Technol.* 4 (2014) 1638–1643.
- [77] H. Morikawa, M. Minamoto, Y. Gorou, J. Yamaguchi, H. Morinaga, S. Motokucho, Two diastereomers of *d*-limonene-derived cyclic carbonates from *d*-limonene oxide and carbon dioxide with a tetrabutylammonium chloride catalyst, *Bull. Chem. Soc. Jpn.* 91 (2017) 92–94.
- [78] S.-Y. Park, H.-Y. Park, H.-S. Lee, S.-W. Park, C.-S. Ha, D.-W. Park, Synthesis of poly [(2-oxo-1,3-dioxolane-4-yl) methylmethacrylate-co-ethyl acrylate] by incorporation of carbon dioxide into epoxide polymer and the miscibility behavior of its blends with poly(methyl methacrylate) or poly(vinyl chloride), *J. Polym. Sci. Part A: Polym. Chem.* 39 (2001) 1472–1480.
- [79] M. Lv, P. Wang, D. Yuan, Y. Yao, Conversion of carbon dioxide into oxazolidinones

- mediated by quaternary ammonium salts and DBU, *ChemCatChem* 9 (2017) 4451–4455.
- [80] S. Liu, N. Suematsu, K. Maruoka, S. Shirakawa, Design of bifunctional quaternary phosphonium salt catalysts for CO₂ fixation reaction with epoxides under mild conditions, *Green Chem.* 18 (2016) 4611–4615.
- [81] Y. Wu, Y. Zhao, R. Li, B. Yu, Y. Chen, X. Liu, C. Wu, X. Luo, Z. Liu, Tetrabutylphosphonium-based ionic liquid catalyzed CO₂ transformation at ambient conditions: a case of synthesis of α -alkylidene cyclic carbonates, *ACS Catal.* 7 (2017) 6251–6255.
- [82] F.D. Bobbink, D. Vasilyev, M. Hulla, S. Chamam, F. Menoud, G. Laurency, S.A. Katsyuba, P.J. Dyson, Intricacies of cation-anion combinations in imidazolium salt-catalyzed cycloaddition of CO₂ into epoxides, *ACS Catal.* 8 (2018) 2589–2594.
- [83] J. Burt, W. Levason, M.E. Light, G. Reid, Phosphine complexes of aluminium(III) halides – preparation and structural and spectroscopic systematics, *Dalton Trans.* 43 (2014) 14600–14611.
- [84] H.S. Hassan, M.F. Elkady, A.H. El-Shazly, H.S. Bamufleh, Formulation of Synthesized Zinc Oxide Nanopowder into Hybrid Beads for Dye Separation, *J. Nanomater.* 967492 (2014), <https://doi.org/10.1155/2014/967492> 14 pages.
- [85] T.M. Tovar, S.M. Stewart, S.L. Scott, Origin of the ZnCl₂ effect on CH₃ReO₃/c-Al₂O₃ in olefin metathesis, *Top. Catal.* 55 (2012) 530–537.
- [86] D.J. Upadhyaya, S.D. Samant, A facile and efficient pinacol–pinacolone rearrangement of vicinal diols using ZnCl₂ supported on silica as a recyclable catalyst, *Appl. Catal. A: General* 340 (2008) 42–51.
- [87] A. Ma, X. Zheng, S. Wang, J. Peng, L. Zhang, Z. Li, Study on dechlorination kinetics from zinc oxide dust by clean metallurgy technology, *Green Process. Synth.* 5 (2016) 49–58.
- [88] H.-T. Teng, T.-Y. Lee, Y.-K. Chen, H.-W. Wang, G. Cao, Effect of Al(OH)₃ on the hydrogen generation of aluminum–water system, *J. Power Sources* 219 (2012) 16–21.
- [89] S. Kumar, S.L. Jain, B. Sain, Significant rate acceleration in carbonate synthesis from carbon dioxide and oxiranes using dimethyl carbonate as a recyclable medium, *Tetrahedron Lett.* 52 (2011) 6957–6959.
- [90] J. Martinez, J.A. Castro-Osma, C. Alonso-Moreno, A. Rodriguez-Dieguez, M. North, A. Otero, A. Lara-Sanchez, One-component aluminum(heteroscorpionate) catalysts for the formation of cyclic carbonates from epoxides and carbon dioxide, *ChemSusChem* 52 (2017) 1175–1185.
- [91] Y.J. Chen, R.C. Luo, Q.H. Xu, W.Y. Zhang, H.B. Ji, State-of-the-art aluminum porphyrin-based heterogeneous catalysts for the chemical fixation of CO₂ into cyclic carbonates at ambient conditions, *ChemCatChem* 9 (2017) 767–773.
- [92] F. Castro-Gómez, G. Salassa, A.W. Kleij, C. Bo, A DFT study on the mechanism of the cycloaddition reaction of CO₂ to epoxides catalyzed by Zn(Salphen) complexes, *Chem. Eur. J.* 19 (2013) 6289–6298.
- [93] J. Xia, R. Petibon, A. Xiao, W.M. Lamanna, J.R. Dahn, Some fluorinated carbonates as electrolyte additives for Li(Ni_{0.4}Mn_{0.4}Co_{0.2})O₂/graphite pouch cells, *J. Electrochem. Soc.* 163 (2016) A1637–A1645.
- [94] I.A. Shkrob, K.Z. Pupek, D.P. Abraham, Allotropic control: how certain fluorinated carbonate electrolytes protect aluminum current collectors by promoting the formation of insoluble coordination polymers, *J. Phys. Chem. C* 120 (2016) 18435–18444.
- [95] S. Komaba, T. Ishikawa, N. Yabuuchi, W. Murata, A. Ito, Y. Ohsawa, Fluorinated ethylene carbonate as electrolyte additive for rechargeable Na batteries, *ACS Appl. Mater. Interfaces* 3 (2011) 4165–4168.
- [96] M. Takehara, S. Watanabe, N. Nanbu, M. Ue, Y. Sasaki, Synthesis of fluorinated dimethyl carbonates by direct fluorination, *Synthetic Commun.* 34 (2004) 1367–1375.
- [97] Q.-L. Tang, Q.-H. Luo, Adsorption of CO₂ at ZnO: A surface structure effect from DFT + *U* calculations, *J. Phys. Chem. C* 117 (2013) 22954–22966.
- [98] G. Nandi, I. Goldberg, Fixation of CO₂ in bi-layered coordination networks of zinc tetra(4- carboxyphenyl)porphyrin with multi-component [Pr₂Na₃(NO₃)(H₂O)₃] connectors, *Chem. Commun.* 50 (2014) 13612–13615.
- [99] H. Kotsuki, T. Shimanouchi, R. Ohshima, S. Fujiwara, Solvent-free organic reactions on silica gel supports. Facile transformation of epoxides to β -halohydrins with lithium halides, *Tetrahedron* 54 (1998) 2719–2722.
- [100] F. Alonso, Y. Moglie, G. Radivoy, M. Yus, Multicomponent click synthesis of 1,2,3-triazoles from epoxides in water catalyzed by copper nanoparticles on activated carbon, *J. Org. Chem.* 76 (2011) 8394–8405.
- [101] J.W. Comerford, T. Gray, Y. Lie, D.J. Macquarrie, M. North, A. Pellis, *Laminaria digitata* and *Palmaria palmata* seaweeds as natural source of catalysts for the cycloaddition of CO₂ to epoxides, *Molecules* 24 (2019) 269.
- [102] W. Clegg, R.W. Harrington, M. North, P. Villuendas, A bimetallic aluminum(salen) complex for the synthesis of 1,3-oxathiolane-2-thiones and 1,3-dithiolane-2-thiones, *J. Org. Chem.* 75 (2010) 6201–6207.
- [103] C. Beattie, M. North, Titanium(salen)-catalysed synthesis of di- and trithiocarbonates from epoxides and carbon disulfide, *ChemCatChem* 6 (2014) 1252–1259.
- [104] C. Mei, X. Li, L. Liu, C. Cao, G. Pang, Y. Shi, Selectively synthesis of cyclic di- and trithiocarbonates by *N*-heterocyclic carbene/LiCl(Br) catalyzed addition of carbon disulfide to epoxides, *Tetrahedron* 73 (2017) 5706–5714.